

A COMPARATIVE STUDY BETWEEN DISCRETE AND CONTINUUM MODELS TO SIMULATE CONCRETE FRACTURE

Rena C. Yu, Eduardo W.V. Chaves and Gonzalo Ruiz

ETS de Ingenieros de Caminos, C. y P., Universidad de Castilla-La Mancha, 13071 Ciudad Real, Spain

Abstract. We present a comparative study between models that follow the two main trends to study fracture of quasi-brittle materials like concrete. On the one hand we focus on a discrete model that represents the fracture process by cohesive elements that are inserted in the original mesh only when the opening condition is met. Such elements also implement contact and friction algorithms. Besides, mesh size is selected so as to represent the inter-locking effect between the crack surfaces. Everything considered, this approach leads to an explicit and multiscale modeling of fracture. On the other hand we analyze a continuum model based on the strong discontinuity approach. It localizes damage in bands that are narrowed to the limit of having null width and thus simulate the fracture surface. The initiation and propagation processes are modeled by a bifurcation analysis that searches for the surfaces where damage can be localized at every step. Finally, we use both approaches to do 3-D simulations of fracture tests in concrete that allow an evaluation of their relative performance.

Resumen. Esta comunicación estudia comparativamente modelos que siguen las dos tendencias para abordar el estudio numérico de la fractura de materiales cuasi-frágiles como el hormigón. Nos centramos por un lado en un modelo discreto en el que la fractura se representa por medio de elementos cohesivos que se insertan entre los elementos de la malla original a medida que se propaga. Los elementos incorporan algoritmos de contacto y fricción. Además, el tamaño de la malla se selecciona de modo que se reproduzca el efecto de engranaje mecánico entre las superficies rotas. Todo ello hace que el proceso de fractura se simule de modo explícito y que esta aproximación pueda enmarcarse dentro de los modelos multiescala. También analizamos un modelo continuo basado en la aproximación de las discontinuidades fuertes. En ella se localiza el daño en bandas que llegan a tener un ancho nulo y que, consecuentemente, simulan la superficie de fractura. El proceso de iniciación y propagación se simula por medio de algoritmos de bifurcación que identifican las superficies sobre las que se formulan las discontinuidades, lo cual permite ofrecer un modelo autoconsistente. Por último, se presenta una simulación en tres dimensiones de ensayos de fractura de hormigón con objeto de comparar los resultados de ambos métodos.

1 INTRODUCTION

Since linear elastic fracture mechanics showed its limitations when applied to high toughness materials (for example, tough steels, which are able to develop large plastic zones near the crack tip before tearing off) or quasi-brittle materials like concrete (whose internal length scale for fracture processes is much larger than for most materials), various approaches have emerged to take into account the nonlinear mechanisms of the fracture process zone.

One straightforward way to deal with the fracture phenomena is the discrete approach, which identifies the new crack as newly-emerged boundaries of the bulk material but still transfers traction in its early stage through a constitutive relation called cohesive law. This methodology was originally applied to ductile fracture by Dugdale and Barenblatt and adapted to concrete by Hillerborg and his coworkers (Hillerborg *et al.* 1976 [1]; Hillerborg 1985

[2]). It provides clear criteria for fracture initiation and growth, but the insertion of cracks represents a topological problem that is not easy to handle. For long years cohesive models were restricted to modeling cracks whose path was known *a priori*. There were also attempts of studying fracture processes with multiple cracks by embedding the cohesive elements into the mesh from the very beginning of the calculation, but such procedure was a source of numerical instabilities (Planas, 2003 [3]). Pandolfi and Ortiz ([4], [5]) came up with a fragmentation algorithm that solved the problem by inserting cohesive elements when and where they are needed. In principle it restricts the possible crack path to pre-existing element boundaries, although this hindrance can be overcome by using remeshing procedures. The versatility of the cohesive fracture model plus the fragmentation algorithm used for propagating dynamic cracks has been well demonstrated by Ortiz and his coworkers (see Camacho and Ortiz, 1996 [6]; Ortiz and Pandolfi, 1999 [7]; Ruiz *et al.* 2000 [8]; Ruiz *et al.* 2001 [9]; Pandolfi *et al.* 2000

[10]; Yu *et al.* (2002) [11]). So we would like to consider the fragmentation algorithm as part of the discrete cohesive fracture model which we are going to abbreviate as DCFM from now on. The simplicity of the model and its compatibility with the standard finite element framework make it very attractive for studying complex fracture processes.

An alternative way of looking at fracture is to incorporate strain or displacement discontinuities into standard finite element interpolations. The development of such techniques was pioneered by the work of Ortiz (Ortiz *et al.*, [12]). His work triggered the development of various powerful methods that allow the efficient modeling of regions with highly localized strains (see Jirásek [13], for a systematic comparative study of embedded-crack modeling). One of them, termed as the strong discontinuity approach (SDA), considers fracture as the limit case of a strain localization in a band of null bandwidth. The SDA refers to the capture of jumps in the displacement field (strong discontinuities) by using standard solid mechanics models equipped with stress vs. strain relationships (continuum constitutive equations). By identifying the main features that make the standard constitutive equations consistent with the appearance of strong discontinuities, going through the process of re-evaluating the kinematics to include the discontinuous displacement fields, enhanced strain fields, the SDA naturally brings on its link with the cohesive fracture mechanics (Oliver *et al.*, 2000 [14]). Discrete constitutive models are automatically induced through a continuum damage model in the 1D case. For general 2D-3D cases, the weak discontinuity concept is introduced to precede the strong discontinuity condition and at the same time connects with the physics of the fracture process zone. Another way of embedding strong discontinuities is the recently developed extended finite element method (termed XFEM; for instance, see Melenk and Babuska, 1996 [15]; Moës and Belytschko, 1999 [16] or Chessa and Belytschko, 2003 [17]), which utilizes nodal enrichments of the displacement field based on a local partition of unity. It was motivated by minimizing re-meshing; efforts are therefore devoted to various enrichment techniques (Belytschko, 2003 [18, 19]) to resolve the crack initiation and propagation.

In this paper we are going to focus on two advanced models that are quite representative of their respective class: the discrete cohesive fracture model accompanied by the fragmentation algorithm (DCF) and the strong discontinuity approach (SDA) embedded into the element formulations. In particular, we are interested on how do the two models tackle the initiation and propagation of cracks in a quasi-brittle material like concrete.

The organization of the rest of the paper is as follows. The boundary value problem for a cracked body is presented in Section 2; a brief review of both models is depicted in Section 3. Numerical examples applied to frac-

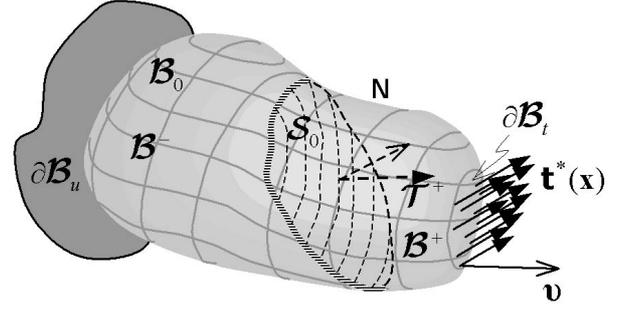


Figure 1: Three dimensional body and discontinuity interface S_0 .

ture in concrete are presented in Section 4. Finally in Section 5 some conclusions are drawn.

2 THE BOUNDARY VALUE PROBLEM (BVP)

By way of a general framework, we start by considering a deformable body occupying an initial configuration $B_0 \subset \mathbb{R}^3$. The boundary of the body is partitioned into a displacement boundary ∂B_u and a traction boundary ∂B_t . The body undergoes a motion described by a deformation mapping $\varphi : B_0 \times [0, T] \rightarrow \mathbb{R}^3$, where $[0, T]$ is the duration of the motion, under the action of body forces $\rho_0 \mathbf{b}$ and prescribed boundary tractions \mathbf{t}^* applied over ∂B_t . The attendant deformation gradients are denoted \mathbf{F} and the first Piola-Kirchhoff stress tensor \mathbf{P} . In addition, the solid contains a collection of cohesive cracks (or displacement discontinuities). The locus of these cracks on the undeformed configuration is denoted S_0 , Fig. 1.

Under these conditions, the weak form of linear momentum balance, or virtual work expression, takes the following form:

$$\int_{B_0} [\rho_0 (\dot{\mathbf{b}} - \ddot{\varphi}) \cdot \boldsymbol{\eta} - \mathbf{P} \cdot \nabla_0 \boldsymbol{\eta}] dV_0 - \int_{S_0} \mathbf{t} \cdot \llbracket \boldsymbol{\eta} \rrbracket dS_0 + \int_{\partial B_t} \mathbf{t}^* \cdot \boldsymbol{\eta} dS_0 = 0 \quad (1)$$

where a superposed dot denotes the material time derivative, ∇_0 is the material gradient, $\boldsymbol{\eta}$ is an arbitrary virtual displacement satisfying homogeneous boundary conditions on ∂B_u , \mathbf{t} is the cohesive traction over S_0 , and $\llbracket \cdot \rrbracket$ denotes the jump across an oriented surface.

3 HOW DOES EACH MODEL SOLVE THE BVP?

3.1 The discrete cohesive fracture model + the fragmentation algorithm

From Eq. (1), it is clear that the presence of a cohesive surface results in the addition of a new term to the virtual work expression. In order to complete the definition

of the problem, a set of constitutive relations for the cohesive tractions \mathbf{t} has to be provided, in addition to the conventional constitutive relations describing the bulk behavior of the material.

Ortiz and Pandolfi (1999) [7] postulated a general form of a free energy density ϕ per unit undeformed area over S_0 , which is a function of the opening displacements, the local temperature, some suitable collection of internal variables describing the current state of decohesion of the surface, as well as the unit normal \mathbf{n} to the cohesive surface in the deformed configuration. The explicit dependence of ϕ on \mathbf{n} is required to allow for differences in cohesive behavior for opening and sliding.

A potential structure of the cohesive law furnishes its scalar dependence on the free energy density ϕ . By assuming that ϕ depends on the opening displacements only through an effective opening displacement and, at the same time, introducing a parameter β which assigns different weights to the sliding and normal opening displacements, a simple class of mixed-mode cohesive laws accounting for tension-shear coupling (see Camacho and Ortiz [6]) is obtained:

$$\mathbf{t} = \frac{t}{\delta} (\beta^2 \delta_s \mathbf{s} + \delta_n \mathbf{n}), \quad (2)$$

where

$$t = \sqrt{\beta^{-2} t_s^2 + t_n^2} \quad (3)$$

$$\delta = \sqrt{\beta^2 \delta_s^2 + \delta_n^2} \quad (4)$$

The unit vector of the tangential direction of the displacement jump is denoted by \mathbf{s} ; t_s and t_n are the shear and the normal traction components, respectively and t is an effective cohesive traction; δ_s and δ_n are the sliding and the opening components of the displacement jump, and δ is an effective opening displacement. The two effective quantities are going to be related by an irreversible cohesive law, say, for example, Fig. 2.

Contact and friction are regarded as independent phenomena to be modelled outside the cohesive law. Notice that the presence of friction may significantly increase the sliding resistance in closed cohesive surfaces.

3.1.1 Constitutive models for the bulk material

Cohesive models furnish a complete theory of fracture, and permit the incorporation into the material description of *bona fide* fracture parameters such as the fracture energy and the tensile strength. By focusing specifically on the separation process, a sharp distinction is drawn in cohesive theories between fracture, which is described by recourse to cohesive laws, and bulk material behavior,

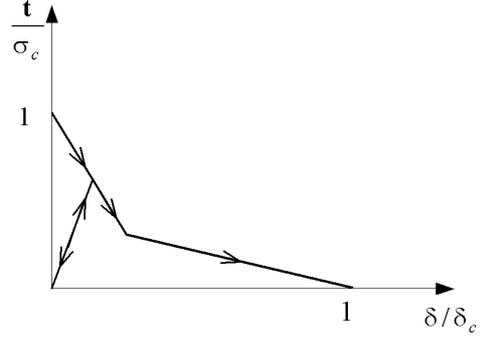


Figure 2: Bi-linear irreversible cohesive law.

which is described through an independent set of constitutive relations. The use of cohesive models is therefore not limited by any consideration of material behavior, finite kinematics, non-proportional loading, dynamics, or the geometry of the specimen.

3.1.2 The crack initiation and propagation

In calculations, decohesion is allowed to occur along element boundaries only. Initially, all element boundaries are perfectly coherent (and all of them could be considered as possible cracks) and the elements conform in the usual sense of the displacement finite element method. When the critical value for the effective cohesive traction is attained at the interface between two volume elements, a cohesive element is inserted using a fragmentation algorithm (Pandolfi and Ortiz, 2002 [5]) at that location. The cohesive element with its proper cohesive law subsequently governs the opening of the cohesive surface.

The crack propagation and initiation are not considered as distinct events in the DCFE. For each loading step, the fragmentation algorithm checks for possible cracks. Thanks to this feature, the initiation and nucleation of cracks can be predicted with ease.

3.2 The strong discontinuity approach

Originated from its precedence strain localization, the main goal of SDA has been to approach the limit case of a strain localization in a band of null bandwidth, whereas the general strain localization case is matched by a weak discontinuity, characterized by continuous displacement fields and discontinuous but bounded strain fields which localize in a band of finite bandwidth. See Simo and Rifai (1990), Simo *et al.* (1993), Simo and Oliver (1994), Oliver *et al.* (2002) [20, 21, 22, 23].

3.2.1 Constitutive model for the bulk material

The SDA was introduced as a basic tool to derive a general framework in which different families of constitutive equations for bulk materials can be adopted, Oliver (1996) [24]. For inelastic quasi-brittle materials an isotropic damage model is often adopted. The term damage mechanics has been used to refer to models that are characterized by a loss of stiffness or a reduction of the secant constitutive modulus. First introduced by Kachanov (1958) [25] along the concept of effective tension, the damage variable was treated as a scalar (isotropic damage), whose value ranged from 0 to 1. More details about this model can be found in Chaboche (1979), Carol *et al.* (1998), Oliver *et al.* (1990) [26, 27, 28]. A representative continuum damage model in the finite deformation range is presented in Oliver *et al.* (2003) [29], in which a free energy density function in terms of the deformation gradient tensor and a set of internal variables is defined. The constitutive equation is presented through a scalar strain-like internal variable r and a stress-like internal variable q . The variable r determines the damage level of the material through the damage variable $d = 1 - q(r)/r$, and $q(r)$ sets the evolution of the elastic domain through a damage function. The rate form of the softening law is defined through the softening modulus as

$$\dot{q} = \mathcal{H} \dot{r}. \quad (5)$$

In terms of the stress-strain response, four distinct loading phases can be identified, see Figs.3 and 4.

I. Elastic phase: the stress-state before the point Y (the yielding point in plasticity, the initiation of inelastic behavior in general inelastic solids). In this phase the material obeys generalized Hooke's law.

II. Inelastic phase: the state between point Y and B . B is the bifurcation point when the general bifurcation conditions (the loss of uniqueness) is achieved. The hardening/softening modulus takes the value \mathcal{H}_Y , the material behavior is still continuous.

III. Weak discontinuity phase: the state up to point SD . From the mechanics viewpoint, the weak discontinuity regime defines a zone where the discontinuity is processed. Physically it signals a change in the behavior of the bulk material due to the formation of the fracture process zone. Numerically speaking this transition avoids an unexpected artificial elastic loading (see Oliver *et al.* (2003) [29] for detailed discussion). Finally, from an analytical standpoint, this phase is predicted by a region between the loss of uniqueness (general bifurcations) and the loss of ellipticity (discontinuous bifurcations) of the stress-strain response, see Ottosen and Runesson (1991) [30, 31].

In this stage a variable bandwidth model is activated, whose initial width h_B (Fig. 4), defined as the ratio between a critical softening modulus \mathcal{H}_{crit} and the discrete

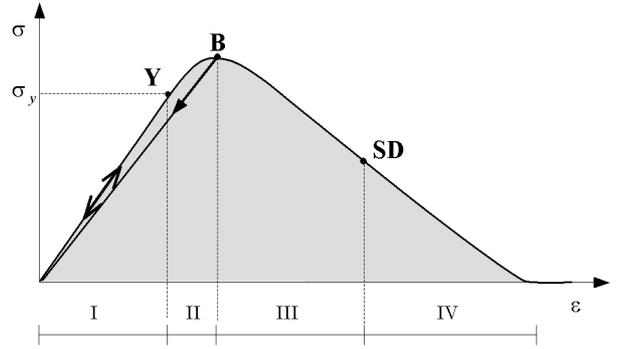


Figure 3: Characteristic points during the loading process.

softening modulus $\bar{\mathcal{H}}$, see Oliver *et al.* (1999) [32], Manzoli (1998) [33], Oliver *et al.* (2000) [14].

IV. Strong discontinuity phase: The point SD corresponds to the onset of the strong discontinuity (the loss of ellipticity of the stress-strain response). It is characterized by the appearance of a jump in the displacement field, Oliver *et al.* (2000) [14].

3.2.2 The fracture initiation

The fracture initiation is identified as the appearance of material instability, or the loss of uniqueness of the solution (point B in fig. 3). In the mathematical sense, this is signaled by the singularity of the characteristic tangent stiffness modulus tensor Q defined as $Q_{il} = n_j D_{ijkl} n_l$ (or the so-called acoustic tensor following the fluid dynamics terminology), where D_{ijkl} is the tangent stiffness tensor, \mathbf{n} is the unit normal vector of the surface S_0 , see Fig. (1). A critical value \mathcal{H} and a critical direction of the discontinuity surface \mathbf{n} are obtained to define the fracture initiation.

3.2.3 The crack propagation

Unlike the DCFE, in which all element boundaries are possible cracks, the SDA needs to define a series of failure surfaces for crack propagation. For this purpose an efficient method called the *overall tracking* has been proposed by Oliver *et al.* (2002) to obtain a continuous failure surface. A family of level curves (in 2D) or level surfaces (in 3D) enveloping the propagation direction can be constructed in analogy to a heat conduction problem. This methodology proves itself a powerful tool especially in simulating multiple cracks (Samaniego and Oliver 2003 [34]).

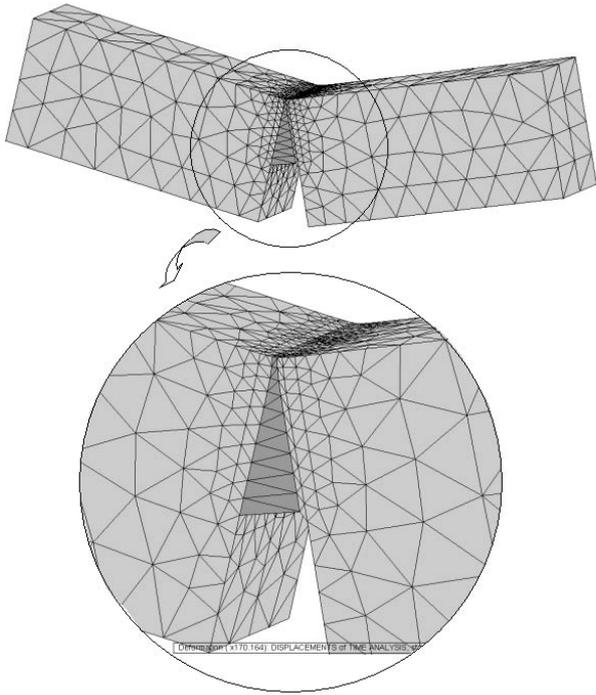


Figure 6: The fracture patterns at loading displacement 0.25 mm.

loading step. The SDA model is more stable for this particular mesh, provided that it allows the crack to be located in the middle of the element. In fact, we have tried an alternative mesh in which the crack surface is fully contained in inter-tetrahedron boundaries and the SDA was not able to get to the peak load. This alternative mesh favors DCFE because it implies a smooth crack propagation. Actually DCFE run up to the insertion of the last cohesive element in this case.

5 SUMMARY AND CONCLUSIONS

We have briefly compared two distinct finite element approaches to non-linear fracture mechanics for quasi-brittle materials like concrete.

On the one hand we have focused on a discrete approach that represents cracks by means of cohesive elements. The model uses a fragmentation algorithm that inserts the cohesive elements within the original mesh where and when the opening condition is met. The elements are also provided with contact and friction routines that enable them to simulate explicitly physical phenomena that may condition the macroscopic response. This also implies that the process zone has to be adequately resolved which may lead to take recourse to re-meshing techniques. It is precisely this kind of topological problems what increases the computational cost and may fade the appeal of the method. This approach to study fracture is compatible with any bulk constitutive law. Indeed, it has been used successfully to simulate both ductile and brittle fracture. The ability of simulating separately events that are

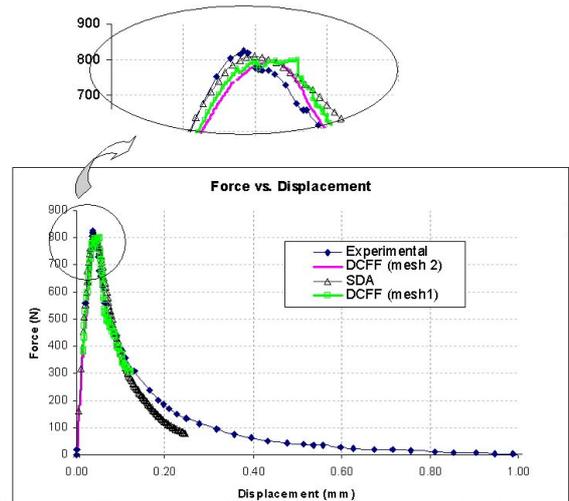


Figure 7: The comparison of the force vs. displacement curves obtained by the DCFE, SDA and the experimental data.

of different nature gives this model a multi-scale character.

On the other hand the strong discontinuity approach studies fracture within a continuous framework. The adjective *strong* refers to the ability of capturing jumps in the displacement field across a surface with zero bandwidth. Doing so implies an enhancement of the kinematics of the governing equations. The strain localization starts when a failure surface is reached in the space of the principal stresses. From then on there is a softening of the properties of the material and a localization of the strain over a band whose width tends to zero, the whole process being controlled by a damage law. The search for the surface that is likely going to hold the fracture in the next step is done by a standard bifurcation analysis.

Both approaches have been used to model a simple mode I TPB test in concrete. The mesh arrangement plays an important role in both models. DCFE works better when element boundaries are placed in the track trajectory (which in this case is known beforehand) and may not converge when dealing with many cracks and fragments. Likewise, SDA prefers mesh orientations that allow the main crack going through the elements and is not able so far to handle multi-cracking processes (in 3D). The element size is chosen in DCFE to represent the aggregate size and consequently works as a material length that determines some of the mechanisms of concrete fracture. SDA uses the width of the weak discontinuity transient zone as a parameter to model the nucleation of the process zone. The results of both models are quite close to their experimental counterparts. Nevertheless, some more cases in a wider variety of geometries and loading conditions should be run in order to complement this study.

6 ACKNOWLEDGMENTS

The authors acknowledge financial support from the *Ministerio de Ciencia y Tecnología* (MCYT), Spain, under grant MAT2003-0843. Rena C. Yu also thanks MCYT for the financial support given under the *Ramón y Cajal Program*, which makes possible her work at the *ETSI de Caminos, C., y P., Universidad de Castilla-La Mancha*.

REFERENCES

- [1] A. Hillerborg, M. Modeer, and P.E. Petersson. Analysis of crack formation and crack growth in concrete by means of fracture mechanics and finite elements. *Cement and Concrete Research*, 6:773–782, 1976.
- [2] A. Hillerborg. Numerical methods to simulate softening and fracture of concrete. *Fracture Mechanics of Concrete. Structural Application and Numerical Calculation*. In G. C. Sih and A. Di Tommaso, editors, *Computational Mechanics. New Trends and Applications. Proceedings (CD-ROM) of the Fourth World Congress on Computational Mechanics (WCCM98)*, pages 141–169. Martinus Nijhoff, Dordrecht, 1985.
- [3] J. Planas, D. Cendon, and J.M. Sancho. Oscilaciones de tensiones y rigidez inicial en elementos de interfaz para simulacion numerica de fisuras cohesivas. *Anales de Mecánica de la Fractura*, 20:119–124, 2003.
- [4] A. Pandolfi and M. Ortiz. Solid modelling aspects of three-dimensional fragmentation. *Engineering with Computers*, 14(4):287–308, 1998.
- [5] A. Pandolfi and M. Ortiz. An Efficient Adaptive Procedure for Three-Dimensional Fragmentation Simulations. *Engineering with Computers*, 18(2):148–159, 2002.
- [6] G. T. Camacho and M. Ortiz. Computational modelling of impact damage in brittle materials. *International Journal of Solids and Structures*, 33 (20-22):2899–2938, 1996.
- [7] M. Ortiz and A. Pandolfi. Finite-deformation irreversible cohesive elements for three-dimensional crack-propagation analysis. *International Journal for Numerical Methods in Engineering*, 44:1267–1282, 1999.
- [8] G. Ruiz, M. Ortiz, and A. Pandolfi. Three-dimensional finite-element simulation of the dynamic Brazilian tests on concrete cylinders. *International Journal for Numerical Methods in Engineering*, 48:963–994, 2000.
- [9] G. Ruiz, A. Pandolfi, and M. Ortiz. Three-dimensional cohesive modelling of dynamic mixed-mode fracture. *International Journal for Numerical Methods in Engineering*, 52:97–120, 2001.
- [10] A. Pandolfi, P. R. Guduru, M. Ortiz, and A. J. Rosakis. Three dimensional cohesive-element analysis and experiments of dynamic fracture in C300 steel. *International Journal of Solids and Structures*, 37(27):3733–3760, 2000.
- [11] C. Yu, A. Pandolfi, D. Coker, M. Ortiz, and A.J. Rosakis. Three-dimensional modelling of inter-sonic shear-crack growth in asymmetrically-loaded unidirectional composite plates. *International Journal of Solids and Structures*, 39(25):6135–6157, 2002.
- [12] M. Ortiz, Y. Leroy, and A. Needleman. A finite element method for localized failure analysis. *Computer Methods in Applied Mechanics and Engineering*, 61:189–2148, 1987.
- [13] M. Jirásek. Comparative study on finite elements with embedded cracks. *Computer Methods in Applied Mechanics and Engineering*, 188:307–330, 2000.
- [14] J. Oliver. On the discrete constitutive models induced by strong discontinuity kinematics and continuum constitutive equations. *International Journal of Solids and Structures*, 37:7207–7229, 2000.
- [15] J.M. Melenk and I. Babuška. The partition of unity finite element method: basic theory and application. *Computer Methods in Applied Mechanics and Engineering*, 139:289–314, 1996.
- [16] N. Moes, J. Dolbow, and T. Belytschko. A finite element method for crack growth without re-meshing. *International Journal for Numerical Methods in Engineering*, 46:131–150, 1999.
- [17] J. Chessa, H. Wang, and Belytschko. On the construction of blending elements for local partition of unity enriched finite elements. *International Journal for Numerical Methods in Engineering*, 57(7):1015–1038, 2003.
- [18] G. Zi and T. Belytschko. New finite elements for XFEM and applications to cohesive cracks. *International Journal for Numerical Methods in Engineering*, 57:2221–2240, 2003.
- [19] T. Belytschko, H. Chen, J. Xu, and G. Zi. Dynamic crack propagation based on loss of hyperbolicity and a new discontinuous enrichment. *International Journal for Numerical Methods in Engineering*, 58:1873–1905, 2003.
- [20] J. Simo and S. Rifai. A class of mixed assumed strain methods and the method of incompatible modes. *International Journal for Numerical Methods in Engineering*, 29:1595–1638, 1990.
- [21] J. Simo, J. Oliver, and F. Armero. An analysis of strong discontinuities induced by strain-softening in rate-independent inelastic solids. *Computational Mechanics*, 12:277–296, 1993.

- [22] J. Simo and J. Oliver. A new approach to the analysis and simulation of strong discontinuities. In Z.P. Bažant *et al.*, editor, *The Fracture and Damage in Quasi-brittle Structures*, pages 25–39. E&FN Spon, 1994.
- [23] J. Oliver, A.E. Huespe, M.D.G. Pulido, and E.W.V. Chaves. From continuum mechanics to fracture mechanics: the strong discontinuity approach. *Engineering Fracture Mechanics*, 69:113–136, 2002.
- [24] J. Oliver. Modelling strong discontinuities in solid mechanics via strain softening constitutive equations. Part I: fundamentals. *International Journal for Numerical Methods in Engineering*, 39:3575–3600, 1996.
- [25] L. M. Kachanov. Time of rupture process under creep conditions. *Inzvestia Akademii Nauk. Otd Tech Nauk.*, 8:26–31, 1958.
- [26] J.L. Chaboche. Le concept de contrainte effective appliqué à l'élasticité et à la viscoplasticité en présence d'un endommagement anitrope. In *Colloque EUROMECH 115*. Grenoble Edition du CNRS., 1979.
- [27] I. Carol, E. Rizzi, and K. Willam. On the formulation of isotropic and anisotropic damage. In de Borst *et al.*, editor, *Computational Modelling of Concrete Structures*, pages 183–192. A.A. Balkema Publishers, 1998.
- [28] J. Oliver, M. Cervera, S. Oller, and J. Lubliner. Isotropic damage models and smeared crack analysis of concrete. In N. Bićanić *et al.*, editor, *Proc.. SCI-C Computer Aided Analysis and Design of Concrete Structure*, pages 945–957. A.A. Balkema Publishers, 1990.
- [29] J. Oliver, A.E. Huespe, M.D.G. Pulido, and E. Samaniego. On the strong discontinuity approach in finite deformation settings. *International Journal for Numerical Methods in Engineering*, 56:1051–1082, 2003.
- [30] N.S. Ottosen and K. Runesson. Properties of discontinuous bifurcation solutions in elastoplasticity. *International Journal of Solids and Structures*, 27(4):401–421, 1991.
- [31] N.S. Ottosen and K. Runesson. Acceleration waves in elastoplasticity. *International Journal of Solids and Structures*, 28(2):135–159, 1991.
- [32] J. Oliver, M. Cervera, and O. Manzoli. Strong discontinuities and continuum plasticity models: the strong discontinuity approach. *International Journal of Plasticity*, 15:319–351, 1999.
- [33] O.L. Manzoli. *Un modelo analítico y numérico para la simulación de discontinuidades fuertes en la mecánica de sólidos*. PhD thesis, Technical University of Catalonia., Barcelona-Spain., 1998.
- [34] E. Samaniego and X. Oliver. *Contributions to the continuum modelling of strong discontinuities in two-dimensional solids*. Monograph CIMNE N-72, ISBN: 84-95999-20-X, Barcelona, Spain, 2003.
- [35] R.C. Yu and G. Ruiz. Modelling of static multi-cracking fracture processes in concrete. In Bićanić *et al.*, editor, *Computational Modelling of Concrete Structures*, pages 149–155. A.A. Balkema Publishers, 2003.
- [36] E.W.V. Chaves and X. Oliver. *A three dimensional setting for strong discontinuities modelling in failure mechanics*. Monograph CIMNE N-73, ISBN: 84-95999-21-8, Barcelona, Spain, 2003.
- [37] G. Ruiz. *Influencia del Tamaño y de la Adherencia en la Armadura mínima de Vigas en Flexión*. Grupo Español del Hormigón, Madrid, Spain, 1998.
- [38] CEB-FIP Model Code 1990, Final draft. Technical Report 203-205, EFP Lausanne, 1991.